

23rd International Convention & Trade Show



**2008 February 28 - March 4
Phoenix, Arizona**

Bentonite HDPE Composite Waterproofing Systems; Below-grade Applications, Failures, and Solutions

Karim P. Allana, PE, RRC, RWC

Allana Buick & Bers, Inc.



Copyright Materials

This presentation is protected by US and International copyright laws.

Reproduction, distribution, display and use of the presentation without written permission of the speaker is prohibited.

Allana Buick & Bers, Inc. 2020



ALLANA BUICK & BERS
Making Buildings Perform Better



Best Practice

Allana Buick & Bers, Inc. (ABBAE) is a Registered Provider with the American Institute of Architects Continuing Education Systems. Credit earned on completion of this program will be reported to CES Records for AIA members. Certificates of completion for non-AIA members are available on request.

This program is registered with the AIA/CES for continuing professional education. As such, it does not include content that may be deemed or construed to be an approval or endorsement by the AIA of any material of construction or any method or manner of handling, using, distributing, or dealing in any material or product. Questions related to specific materials, methods, and services will be addressed at the conclusion of this presentation.



Karim P. Allana, PE, RRC, RWC

- **Education:** B.S., Civil Engineering, Santa Clara University
- **Registration:** P.E., Civil Engineering, California, Washington, Nevada, and Hawaii
- **Certification:** Registered Roof Consultant (RRC), Roof Consultants Institute, and Registered Waterproofing Consultant
- **Overview:**
 - CEO and Senior Principal at Allana Buick & Bers.
 - Former Turner Construction Employee (Project Engineering and Superintendent)
 - Over 37 years experience providing superior technical standards in all aspects of building technology and energy efficiency.
 - Principal consultant in forensic investigations of building assemblies, failure analysis, evaluation and design of building infrastructure and building envelope evaluation and design.
 - Expert in all aspects of building envelope technology.
 - Completed numerous new construction, addition, rehabilitation, remodel and modernization projects for public and private sector clients.
 - Specialization in siding, roofing, cement plaster, wood, water intrusion damage, window assemblies, storefronts, below grade waterproofing, energy efficiency, solar engineering and complex building envelope and mechanical assemblies.



ABBAE Firm Overview

- Allana Buick & Bers (ABBAE) is an Architectural Engineering firm specializing in Building Envelope Systems
- ABBAE is one of the 5 largest building envelope consultants in the country
- ABBAE has over 33 years of experience & over 12,500 projects
- ABBAE is also a leading Forensic Defect firm with hundreds of forensic projects (litigation)
- Locations – 16 offices across California, Nevada, North Carolina, Oklahoma, Oregon, Texas, Virginia, Washington, Colorado and Hawaii



Staff & In-House Expertise

- Licensed Professional Engineers – Civil, Structural, and Mechanical
- Registered Architects
- Building Enclosure Commissioning Process Providers (BECxPs)
- Registered Building Envelope Consultant (RBEC)
- Registered Roofing Consultants (RRCs)
- Registered Waterproofing Consultants (RWCs)
- Registered Exterior Wall Consultant (REWCs)
- Registered Roof Observers (RROs)
- Certified Exterior Insulation and Finish System (EIFS) inspectors
- Curtain Wall Specialists
- ICC Certified Building Inspectors
- Quality Assurance Monitors
- Water Testing Experts
- Leak Investigation and Diagnosis Experts
- Infrared Imaging and Nuclear Moisture Scanning Experts



ABBAE Building Expertise

- Building Envelope Systems
 - Roofing Systems
 - High-Slope/Low-Slope Roofs
 - Green/Garden Roofs
 - Drainage Systems
 - Pedestrian Plazas
 - Exterior Wall Systems
 - Wall Cladding /Siding/GFRC/pre-cast
 - EIFS/cement plaster/stucco
 - Sheet Metal Flashings
 - Windows and Glazing Systems
 - Punched Windows
 - Curtain Wall/Window Wall Systems
 - Sliding Glass Doors
 - Skylights
- Building Envelope Systems (cont'd)
 - Roofing & Waterproofing Systems
 - Deck/Balcony/Lanai Waterproofing
 - Podium Waterproofing
 - Pool/Spa Deck Waterproofing
 - Above-Grade/Below-Grade Waterproofing
 - All types of low and steep sloped roofing
 - Commissioning BECx
 - OPR/BOD/Commissioning Plan
 - Mechanical/HVAC Systems
 - HVAC design
 - Plumbing systems
 - Commissioning and testing



ABBAE Core Services

- Consulting and third-party peer review services
- Engineer of record for building envelope systems
- Contract administration services
- Inspection services (usually direct with owner)
- Air and water performance testing
- Mock-up design, observation, and testing
- Building assessments and forensic investigations
- Litigation support and expert witness services
- Educational seminars with AIA credits



Introduction

Sodium Bentonite based Waterproofing Systems

- Steadily gained popularity for below-grade applications for both blind-side and positive-side construction
- Applications include:
 - Underslab
 - Zero property line (blindside)
 - Back-filled walls
 - Earth-covered structures
 - Tunnels
 - Split-slab deck construction
 - Hydrostatic and non-hydrostatic site conditions



Introduction cont.

Sodium Bentonite based Waterproofing Systems

- Many manufacturers offer a variety of bentonite waterproofing systems
- Some variations include:
 - Standard bentonite sheeting – basic water repulsion
 - Multi-layer sheeting combinations – water & gas repulsion
- Sheeting is designed based on the application



Introduction cont.


Focus of the presentation:

- Soil retention systems and their impact on waterproofing
- Sodium bentonite based waterproofing systems used in blind-side construction
- Different types of blindside construction procedures and how they impact bentonite based waterproofing systems
- Case Study of a failed blindside waterproofing system



History of Sodium Bentonite

- Sodium Bentonite is an absorbent clay that was geologically modified volcanic ash originally deposited in an ancient sea bed as bentonite around 70-74 million years ago

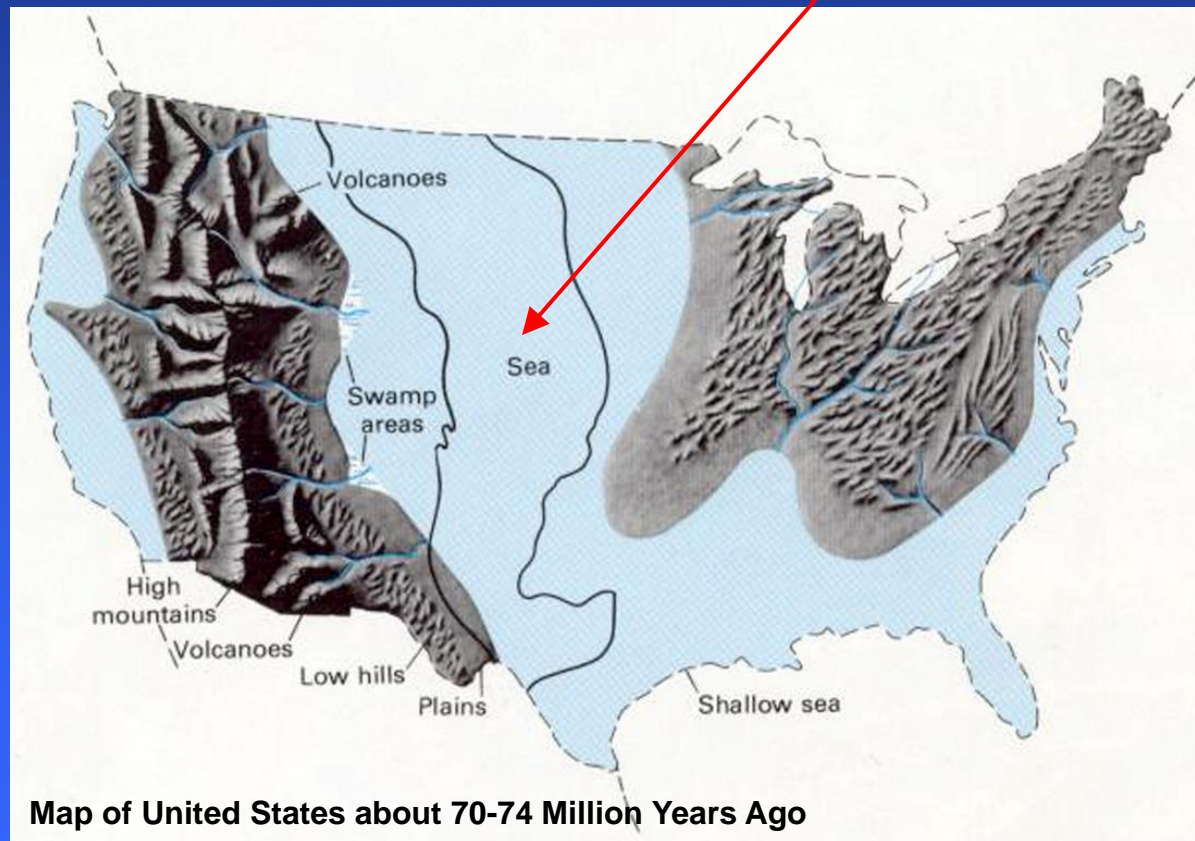

History of Sodium Bentonite Cont.

- Bentonite was named by American Geologist W.C. Knight about 1890
- Discovered in Montana's Rock Creek area at the Benton Formation (a geological stratum at Fort Benton)
- Commercially known as Sodium Bentonite
- Mined in South Dakota and Wyoming
- United States - 2005 top producer world wide with almost 1/3 world share



History of Sodium Bentonite Cont.

Properties of Bentonite

- An absorbent aluminum phyllosilicate generally composed of impure clay
- Two types of Bentonite – swelling (sodium bentonite) and non-swelling (calcium bentonite)
- Sodium bentonite absorbs up to 8x's it's dry mass in water
- Contains exchangeable sodium cations
- Calcium Bentonite can be converted to Sodium Bentonite through “ion exchange”



Bentonite Seals When Wetted Cont.

Sodium Bentonite Granules Transform into a seamless, monolithic membrane to provide an excellent barrier to water

Time Sequence Photography



1. Bentonite Installed Dry




2. Granules quickly transform when wet



3. Seamless Bentonite Membrane



Upon hydration, bentonite extrudes out and seals the overlap seams

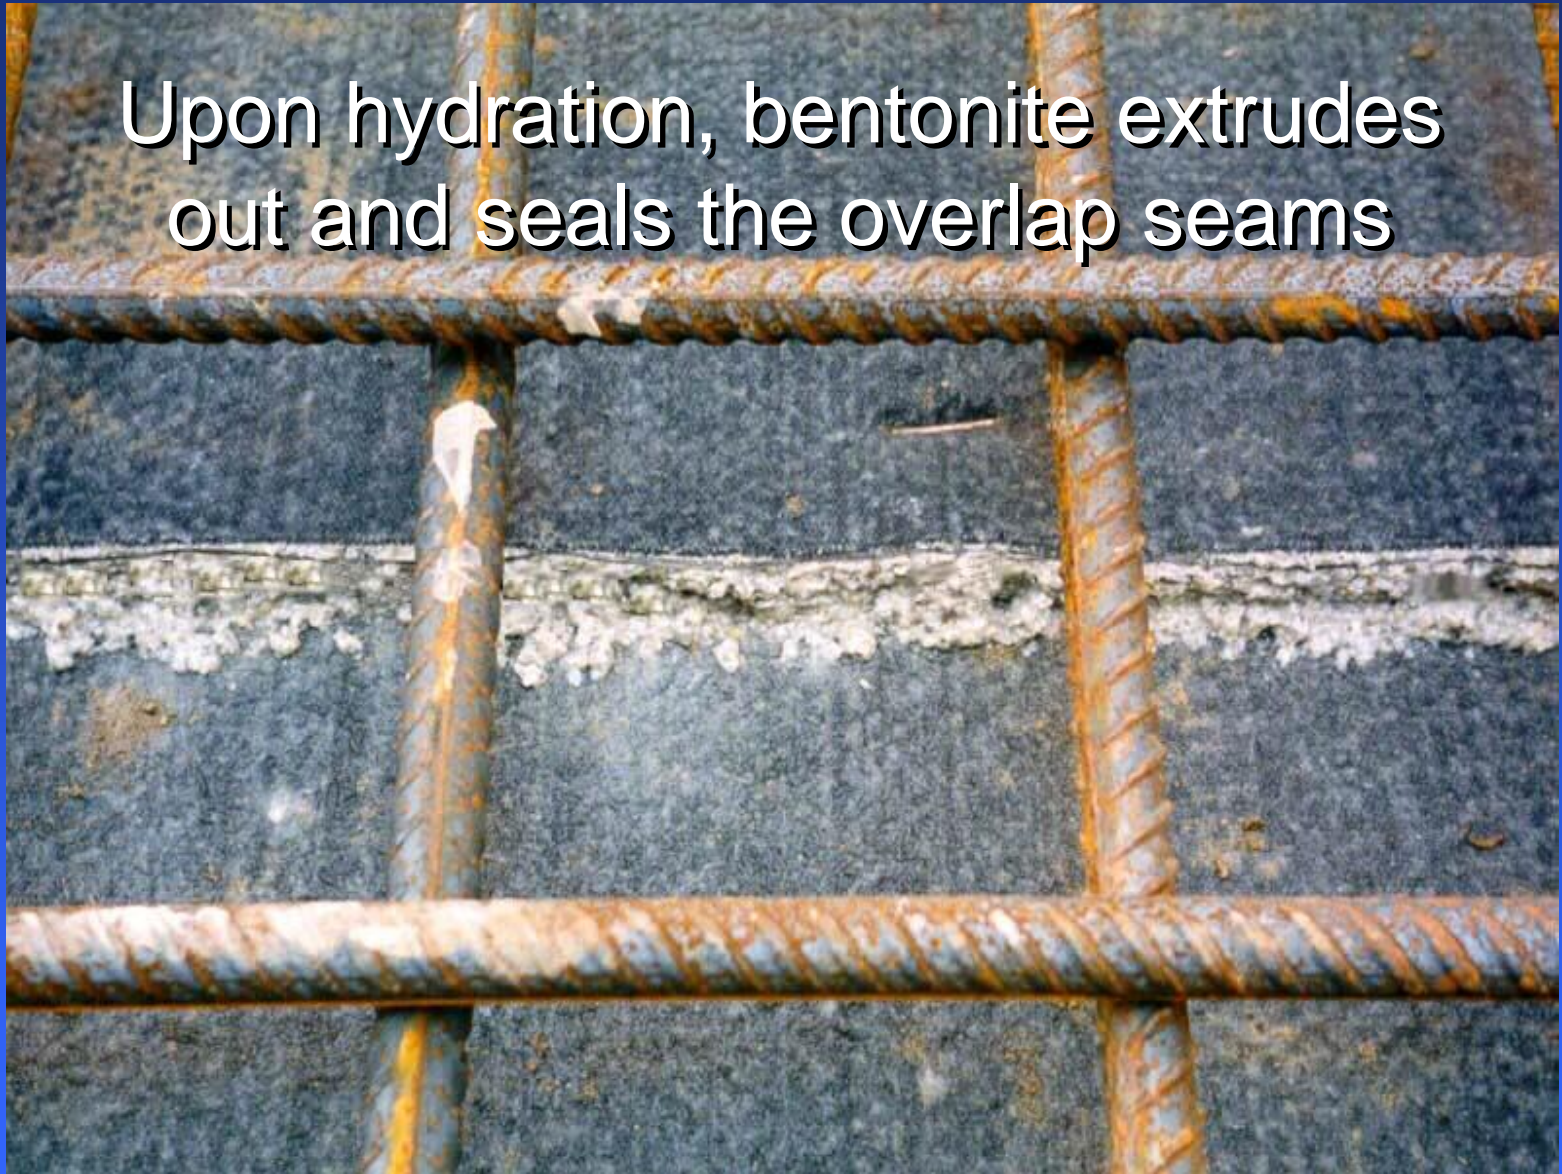

Bentonite is Dispersive

When hydrated, bentonite expands and conforms to irregular surfaces, penetrations, and infiltrates cracks and voids in the concrete



Bentonite is Natural

- Non-toxic
- No Volatile Organic Compounds (VOC's)
- Used in toothpaste, skin lotions, soap, pharmaceuticals, cattle feed, even used to filter fine wines and fruit juices



History of Sodium Bentonite Cont.

The clay of a thousand uses, besides below-grade waterproofing, also used in:

- Drilling mud for oil and gas
- Sealing of sub-surface disposal systems for spent nuclear fuel
- Quarantining metal pollutants of groundwater
- Making slurry walls
- Lining the base of landfills
- Absorbing protein molecules, useful in winemaking



Mining Process

- Mining for Sodium Bentonite is different from traditional mining methods.
- Allows reclamation of the mining site to be restored to it's near original condition
- Begins by removing the overburden with large earth movers
- Overburden is stockpiled
- Bentonite is excavated from bed
- Upon completion, overburden is restored and surface is returned to equal or superior condition



Historical Use in Below-grade Waterproofing

- Introduced as a product in the mid 1920's
- Primarily used in granular form to seal ponds and compacted earth dams until the late 1950's
- Introduced into building waterproofing market in the mid 1960's
- Available product lines included panels, sheets, trowelable, and sprayed forms



Historical Use in Below-grade Waterproofing

Cont.

- Sprayed and trowelable went away due to premature hydration and difficulty in applying uniform thickness
- First commercially available bentonite panel systems were bentonite filled cardboard sheets, which are not widely used today
- Replaced by composite products consisting of a combination of materials, HDPE, geomembranes, or durable textiles
- Composite Materials are:
 - Easier to install
 - Provide better barrier performance



Historical Use in Below-grade Waterproofing

Cont.

- Common forms of bentonite waterproofing products
- granules encapsulated between polypropylene geotextile fabrics
- Laminated to one side of a HDPE geomembrane
- Typical rolls size are 4' wide and vary in length from 15'-24'
- Contains, roughly, 1LB of bentonite per SQ FT
- Both forms are appropriate for blind-and positive-side construction



Soil Retention Systems

- Common soil retention systems include:
- Wood Lagging & Soldier Piles
- Shotcrete Lagging
- Soil Nailing
- Other systems



Original Bentonite Waterproofing System



Positive & Negative Side Waterproofing

- Defined – Positive-side waterproofing is applied to the outside (wet) face of the subsurface building components in contrast to Negative-side waterproofing, which is applied to the inside (dry) face of the subsurface walls and slabs.



Blind-side Waterproofing

- Defined – Blind-side is positive-side
- Blind-side waterproofing systems are required where the exterior faces of foundation walls are not accessible, which requires application of the waterproofing system to the formwork surface facing the excavation.
- This results in the waterproofing's final location to be on the outside of the foundation wall.



When is Blind-side Waterproofing Necessary

- Common situations dictating blind-side waterproofing are:
 - Proximity of adjacent property line, which preclude excavation outside the foundation walls
 - May be more convenient or economical
- Required when concrete foundation is cast against soil retention systems such as wood lagging and soldier piles, steel or wood sheet piling, concrete caisson retaining walls, and slurry or shotcreted rock





Property Line Applications



Earth Retention Systems

- Review different types of Lagging systems used for blind side waterproofing
- Review issues associated with lagging that impact sodium bentonite waterproofing systems




Wood Lagging & Soldier Piles

- Soldier piles, which are heavy, wide flange steel section, are driven into the ground at five to ten foot intervals, depending upon the soil makeup and lagging cross-section. As excavation proceeds, wood lagging is erected in place and tie rods or soil anchors are drilled into the earth for stabilization of soldier piles against soil pressure.



Wood Lagging - Earth Retention System

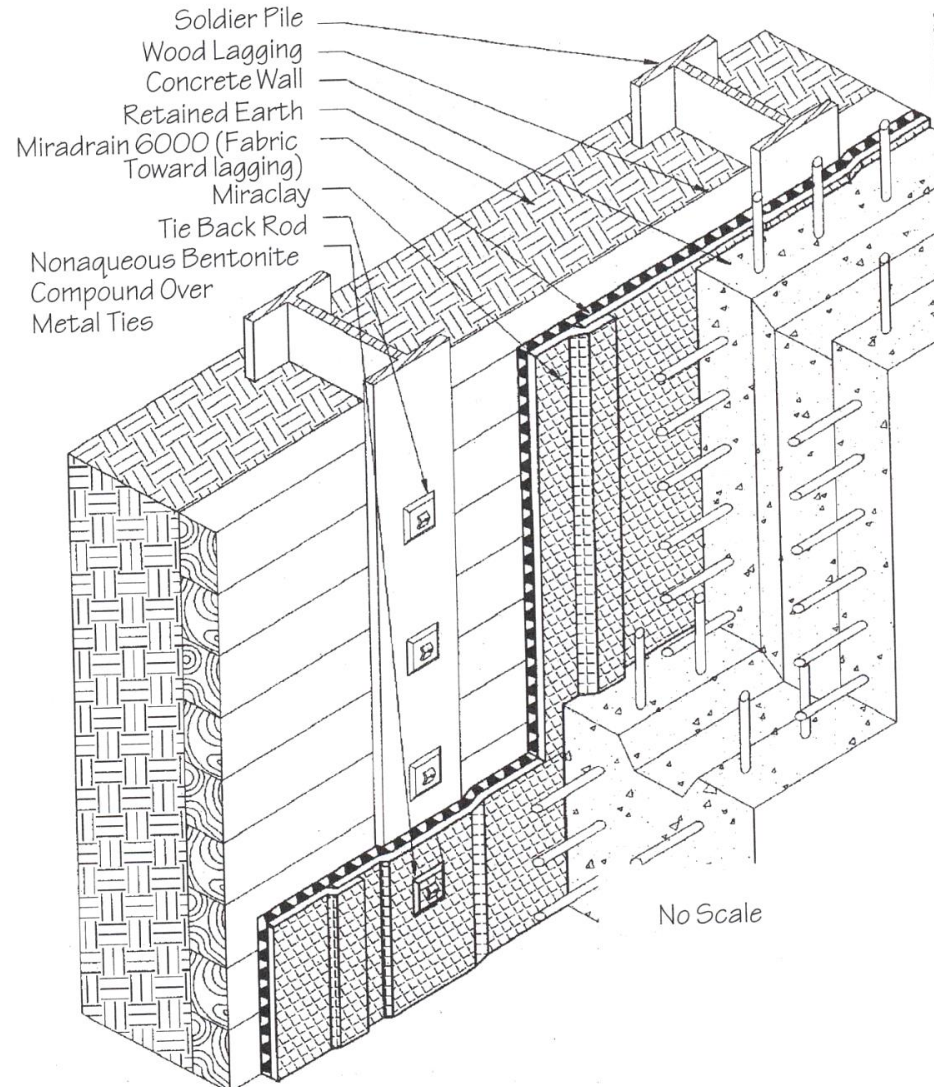


Wood Lagging & Soldier Piles

- WP system is applied directly to the wood lagging and the concrete is poured directly against the WP system.
- Bentonite clay or HDPE composite products are usually specified for this construction process.
- Joints in lagging must be maintained at ½ inch or less. If joints become larger, plywood is typically nailed over lagging or sometimes the gaps are grouted and then waterproofing system is applied.



Conventional Wood Lagging

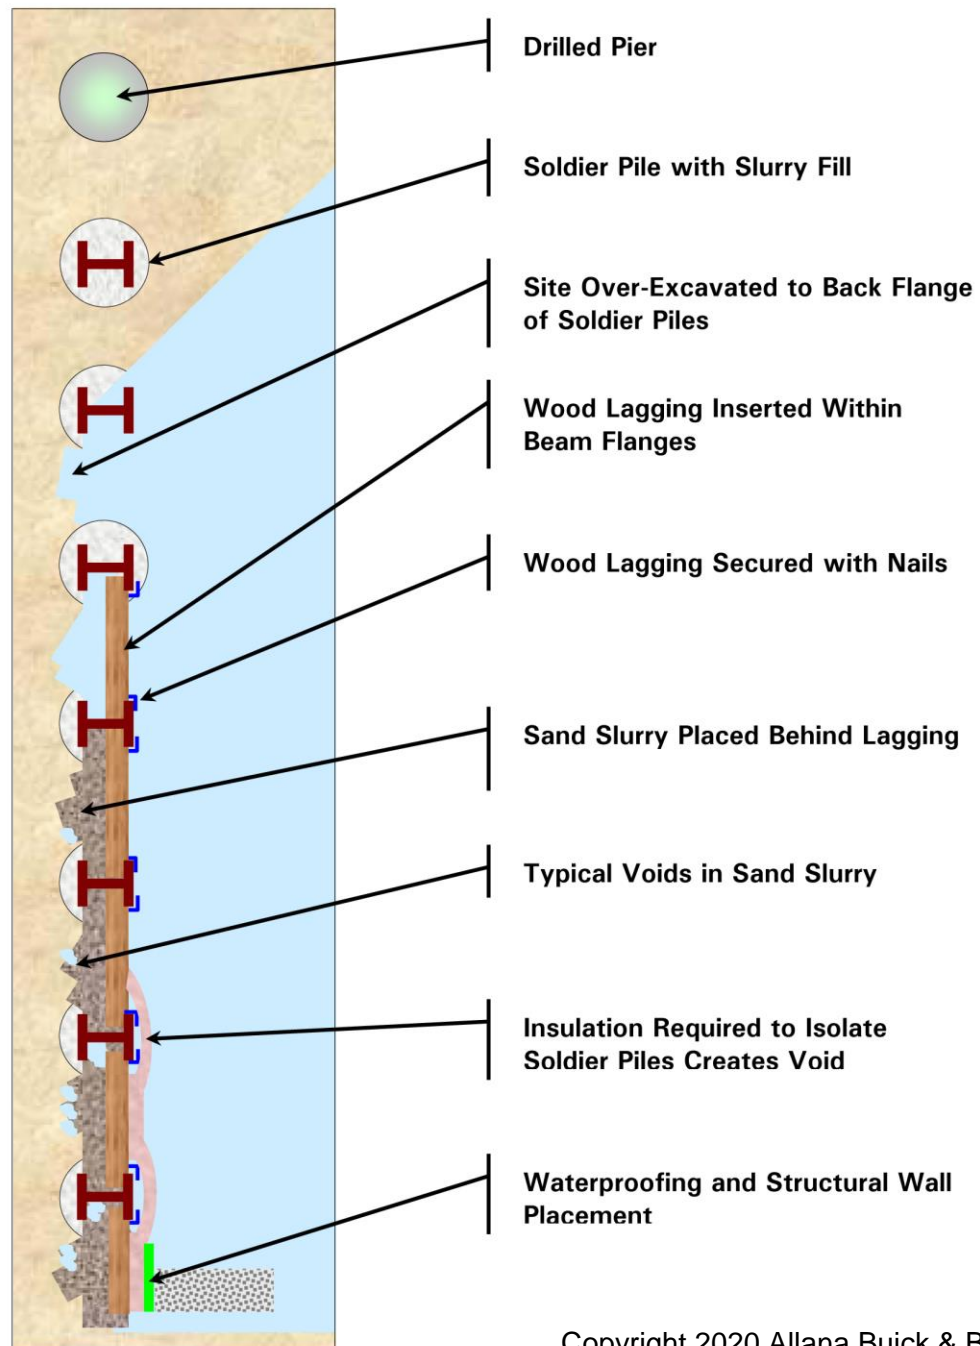


Shotcrete Lagging

- Soldier piles are predrilled at intervals along the wall's baseline. The piles are placed in the hole and backfilled with lean-mix concrete. As the excavation in front of the wall proceeds, shotcrete lagging is installed between the soldier piles in lifts. Tieback anchors may be installed and stressed to provide lateral restraint.



Shotcrete Lagging

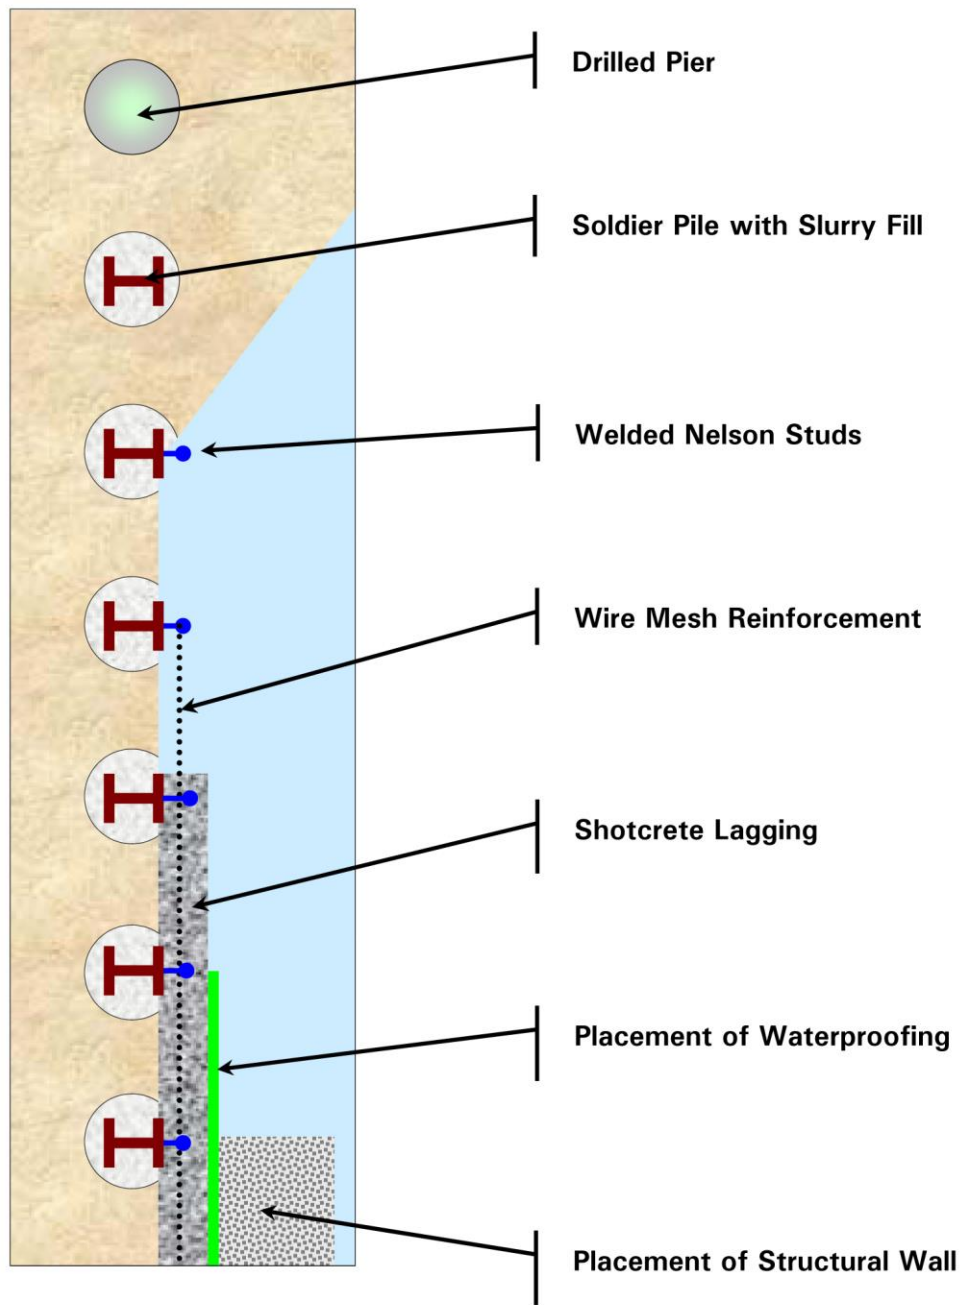



Shotcrete Lagging



Shotcrete Lagging



Soil Nailing

- An insitu reinforcing of the soil while it is excavated from the top down.
- An array of soil nails which are passive inclusions are installed in a grid that functions to create a stable mass of soil.
- In many applications soil nailing can be the least disruptive way to construct a retaining wall.
- Soil Nailing requires an unusual amount of hand work, craftsmanship and geotechnical knowledge to construct.



Other Types of Soil Retention Systems

- Sheet piling
 - Steel sheet piles are long structural sections with a vertical interlocking system that creates a continuous wall.



Other Types of Soil Retention Systems Cont.

- Caissons
 - Series of drilled holes filled with re-enforced concrete that are most often used when shallow, spread footings are not feasible.



Bentonite Waterproofing Systems

- Property-line Construction Applications
- Can be applied as soon as the forms are removed
- Can be installed in freezing weather
- Can seal small cracks
- No special installation equipment required
- Natural mineral – not harmful to the environment
- Self-healing (sealing) characteristics
- No product mixing required by applicator



Included in This Presentation

- Review 2 of the most widely used bentonite systems on the market
- Different makeup of the systems and specific uses
- Benefits and Limitations
- Author not endorsing any product or system



Sodium Bentonite Limitations.

Inherent limitations of Bentonite HDPE

- Application in brackish or slightly salt groundwater
- Standing water during construction – premature hydration
- Over snow – premature hydration
- Requires compaction/confinement to be effective – a minimum of 24 psf is required



Commercial Bentonite/HDPE Products

Product Reviewed :

- Tremco - Paraseal LG
 - Multi-layer sheet membrane waterproofing system
- CETCO – Volclay Voltex DS
 - Interlocking Geotextile waterproofing panel system



Tremco – Paraseal LG

- Multi-layer (3-layer) sheet membrane waterproofing system
 1. Consists of self-sealing, expandable layer of granular bentonite
 2. Bentonite layer is laminated to HDPE sheet
 3. Covered with a protective layer of spun polypropylene
- Controlled thicknesses of 170 mils to 200 mils
- Designed for blind-side installations



Tremco – Paraseal LG Cont.

Blindside application

- Applied before walls are poured
- Designed to resist damage from:
 - Some exposure to inclement weather
 - Normal concrete pours
 - Direct installation of shotcrete
- Can be used in hydrostatic head conditions



Prehydration Due to Rain can Lead to Failure



Tremco – Paraseal LG Cont.

Installation in Lagging (blindsided) Applications

- All installations have bentonite side facing concrete to be waterproofed
- Critical all voids/spaces between lagging and soil are grouted or filled with sand to achieve confinement
- Can be installed vertically or horizontally
 - Cast-in-place – overlap 3” shingle fashion (top over bottom when pouring against)
 - Shotcrete – overlap 4” shingle fashion (bottom over top) when shotcreting against
- Fasten all seams at 4”
- Apply paramastic around tiebacks and penetrations



Tremco – Paraseal LG Cont.

Additional Specifications

- HDPE Laps can be sealed with butyl tape for gas membrane and additional level of waterproofing
- Penetrations need to be detailed properly
- Puncture resistant HDPE liner of 169 lb point load
- Protect from moisture during storage.
Do not double stack



Typical Paraseal Membrane Application



Seam Tape Being Applied







Witches Hat Over a Tieback Head

- The penetration is detailed with Parastick n' Dry (bentonite waterstop), and the witches hat (molded polyethelyne) is filled with Paramastic
- The hat is nailed over the tieback, and another target sheet of Paraseal is installed over it
- Double protection of bentonite.



Paraseal Tie-Back Detail





- The penetration is detailed with Parastick n' Dry (bentonite waterstop),





The witches hat (molded polyethelyne) is filled with Paramastic and the hat is nailed over the tieback





Another target sheet of Paraseal is installed over it



Another target sheet of Paraseal is installed over it.....



.....and nailed



CETCO – Volclay Voltex DS

- Interlocking Geotextile Waterproofing System
 1. Comprised of two high-strength geotextiles sandwiching bentonite, which are interlocked through a needle punching process
 2. Includes a integrated polyethylene liner for added protection and vapor barrier
- Sandwiches 1.10lbs of bentonite per square foot
- Designed for waterproofing under slabs and blind-side applications



CETCO – Volclay Voltex DS_{Cont.}

- Can be installed directly over a properly prepared substrate without the need of a concrete mud slab
 - Although mud slab does provide a more consistent and sound substrate
- Durable composite construction resists damage
 - Although a 3” protection slab can be provided for better under-slab protection



CETCO – Volclay Voltex DS Cont.

- Blindside applications
- Installed against the retention wall
- Concrete is poured against it using a single-sided form
- Recommended for shotcrete application that 2 layers of bentonite be used
 - Cardboard type panel +Voltex DS



CETCO – Volclay Voltex DS_{Cont.}

Installation

- Woven geotextile side is installed facing installer
- Shotcrete is shot against geotextile side
- Panels are secure with washer head mechanical fasteners
- Can be installed to green concrete without primers or adhesives
- Can be installed in freezing or slightly damp conditions



CETCO – Volclay Voltex DS_{Cont.}

- Unique Design Feature
- Concrete/shotcrete clings to geotextile fibers
- Allows waterproofing panels to stay in place, against concrete and shotcrete walls
- Designed only for below-grade waterproofing applications



VOLTEX DS


CROSS-SECTION ILLUSTRATION

HDPE LINER

NON-WOVEN FABRIC

**GRANULAR BENTONITE
1.1-LBS./SF**

WOVEN FABRIC

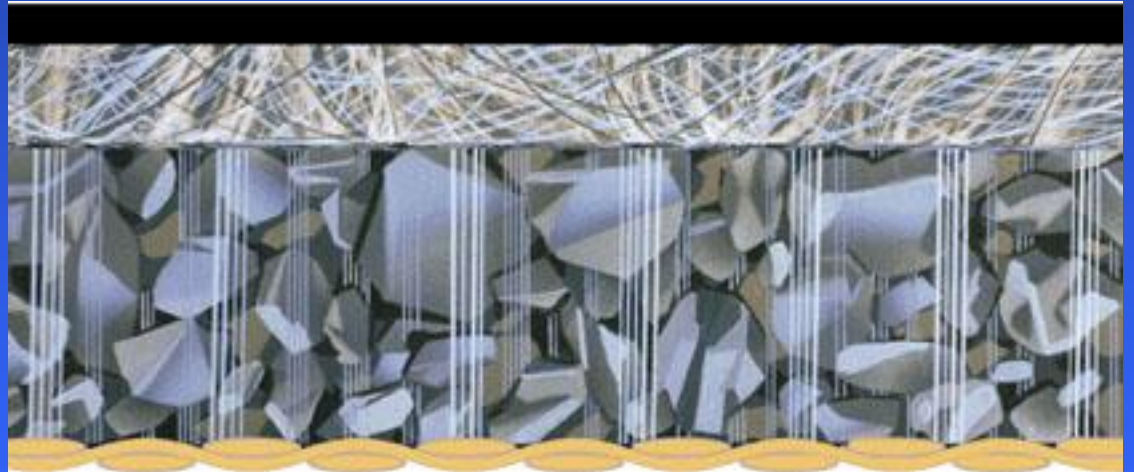

VOLTEX DS®

BENTONITE GEOTEXTILE WATERPROOFING WITH INTEGRATED HDPE LINER



**VOLTEX IS FASTENED TO
CONCRETE FOUNDATION
WALLS WITH WASHER-HEAD
FASTENERS POSITIONED
24" ON CENTER**



VOLCLAY VOLTEX **UNDERSLAB INSTALLATION** **OVER A MUD SLAB**



VOLCLAY VOLTEX **UNDERSLAB INSTALLATION OVER** **COMPACTED EARTH SUBSTRATE**



VOLCLAY VOLTEX **UNDERSLAB INSTALLATIONS**



VOLCLAY VOLTEX **CONCRETE FOUNDATION** **WALL APPLICATION**





VOLCLAY VOLTEX METAL SHEET PILING APPLICATION



Paraseal / Voltex Comparison

TECHNICAL DATA		
Physical Properties Method	Paraseal LG Value	Voltex Volclay Value
Tensile Strength: Membrane (PSI)	4,000 PSI (27.6MPa)	N/A
Resistance to microorganisms (bacteria, fungi, mold, yeast)	unaffected	unaffected
Elongation-ultimate failure of membrane	700%	N/A
Puncture Resistance	169 lbs (76.6kg)	140 lbs (63.5kg)
Hydrostatic Pressure Resistance	150 Ft (45.6m)	231 ft. (70 m)
Resistance to water migration under membrane: zero leakage	150 Ft (45.6m)/Head	150 Ft (45.6m)/Head
Grab Tensile Strength	N/A	95 lbs. (422 N)
Permeance	2.7x10 ⁻¹³ cm/sec	1 x 10 ⁻¹⁰ cm/sec.
Installation Temperatures	-25°F to 130°F (-31.7°C to 54.4°C)	
Low Temperature Flexibility	No effect before or after installation	Unaffected at -25°F (-32°C)

Source, Manufacturer's published data



Project Case Study

- Forensic Case Study Sunnyvale, California
- Waterproofing failure of Downtown Sunnyvale Garage
- Work performed for a construction defect litigation case
- Bentonite/HDPE composite system was installed and had failed
- 2nd largest below-grade structure in Northern California
- Largest below-grade waterproofing repair of it's kind in California



Project Case Study Cont.

- Structure experience extensive leaking throughout below-grade perimeter walls
- Built on zero lot line with shotcrete foundation walls against wood lagging and soldier pile retention walls



Project Case Study Cont.

- Core samples taken from 18" thick shotcrete walls
- Partial excavation behind lagging
- Reviewed original construction drawings
- Reviewed lagging installation photos
- Reviewed soil consolidation
- Visual observations of leaks and water testing



Garage Structure is 2 stories Below the Water Table



Downtown Sunnyvale Garage Leaked Throughout From Day 1



Chemical Grout was Injected 24" O.C.

Injection ports



Project Case Study Cont.

Repairs included:

- Drilling 5/8" diameter holes on a 4' on center grid formation through 18" thick shotcrete foundation wall
- Several types of hydro-active grouts were injected through the holes





Repair work in progress

Typical Injection Equipment



The Repair of Failed Garage Cost Over \$3M



Grout Creates a “Curtain” Behind Concrete



Foam Sometimes Leaves a Mess




Concrete Cores Were Taken To Assess Performance



Cores Showed Large Voids Behind Shotcrete



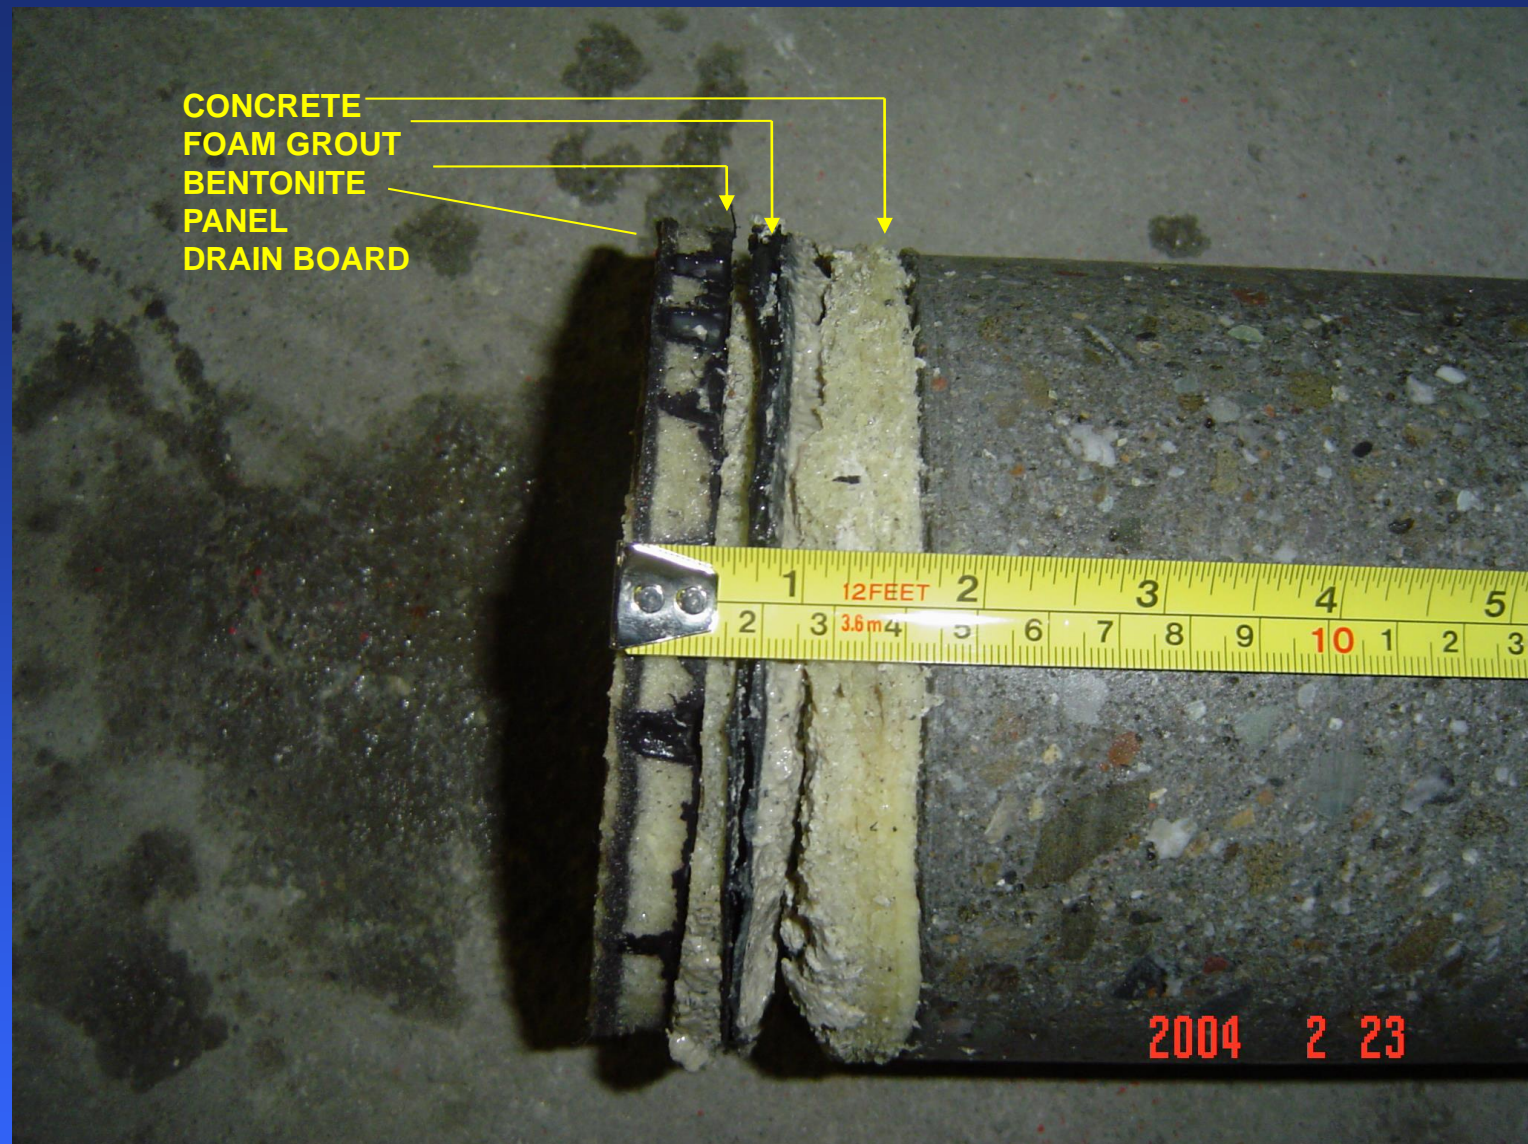

Voids were present on both sides of the retaining wall and ranged from 1" thick to up to 4" thick. Grout in post-repair picture shows measurable void.



Site was Excavated to Forensically Analyze Failure



Site was Excavated to Forensically Analyze Failure



Hydrated Bentonite



Hydrated Bentonite



Seams in Membrane Were Sealed With Butyl Tape



Gap Between Lagging and Shotcrete



Wood Lagging Issues with Bentonite



Excavation of the soil behind the wood lagging revealed that once the wood gets wet, it swells, bends and twists, especially if there are voids between the soil and wood.



Voids at Solder Piles



Void between solder pile and foam protection board was also evident and may have contributed to the failure of the bentonite waterproofing system.






Void behind foam protection board



Void Behind Protection Board



Section of Concrete Was Jack Hammered and Removed Inside

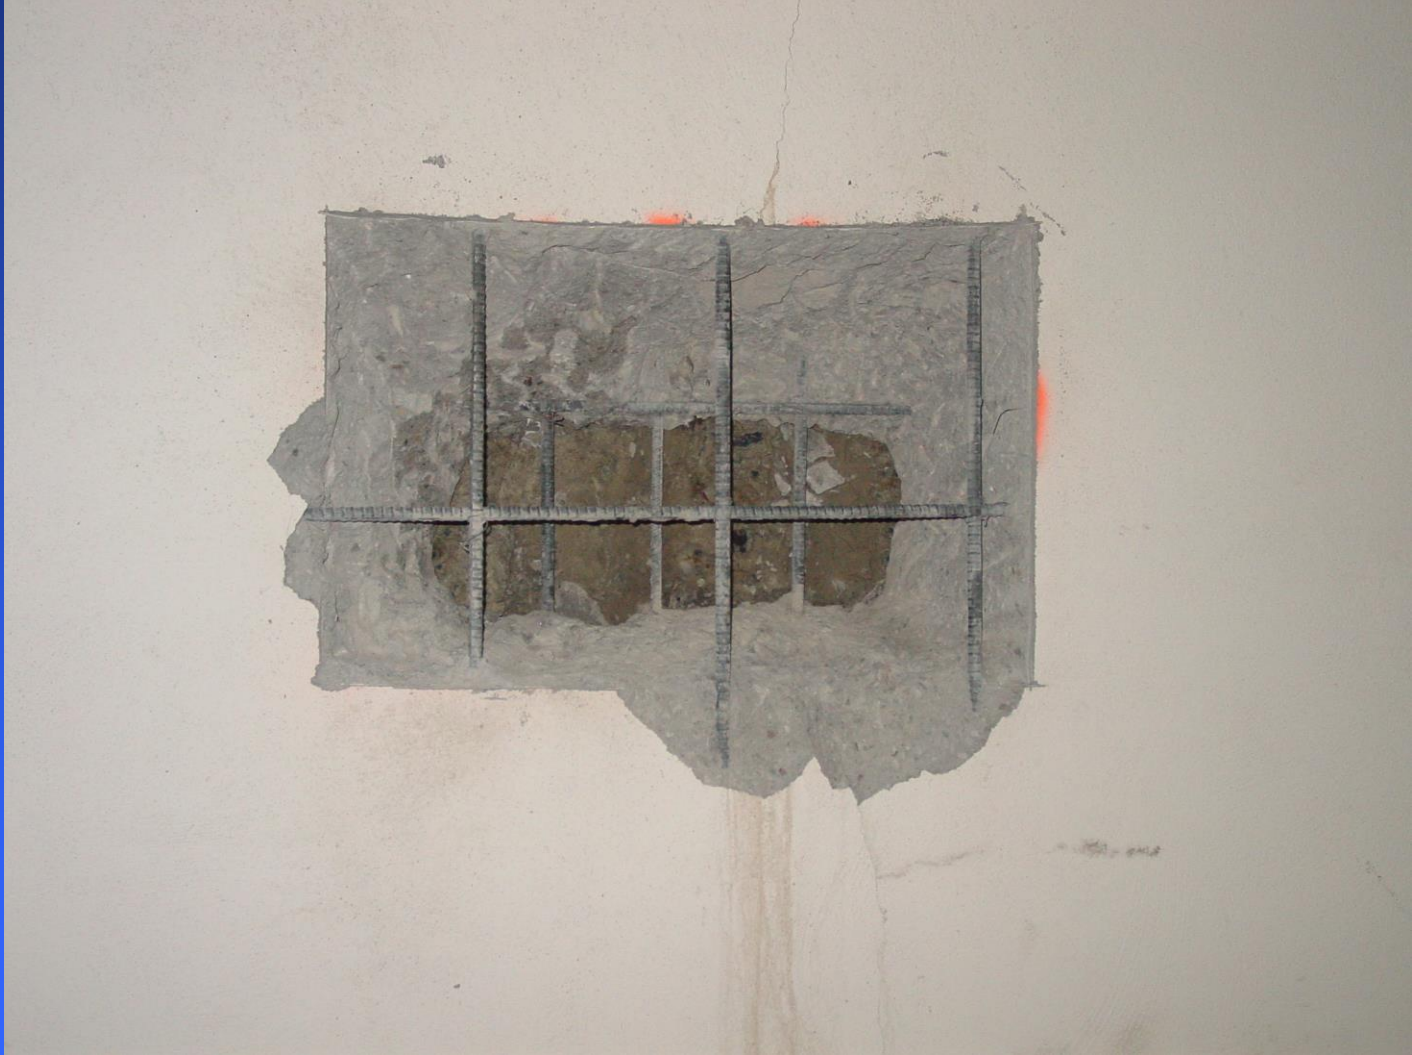

Found Some Laps in Membrane Where Butyl Tape Had Failed



Lessons Learned from Failure

- Bentonite requires confinement to work
- Wood lagging can have gaps and voids in the behind it which can allow lagging to move back
- Wood twists and cups when it gets wet, leaving voids
- Protection board at soldier pile left voids and potentially reduced the system's effectiveness



Project Case Study Cont.

- Grout Characteristics
- Quickly expands and cures upon contact with water to form a water barrier behind the surface of the wall and under portions of the slab
- Designed to fill an voids behind foundation wall
- Upon reaching maximum confinement, grout continues to internally expand thus increasing in density



Project Case Study Cont.

- Case Study Conclusion
- Potential factors in failure
 - Cast-in-place concrete
 - Lagging
 - Soil consolidation
- Care must be taken to fill voids behind lagging to ensure good consolidation
- Lessons learned – led to change in manufacturers specifications



Presentation Conclusion

Sodium Bentonite is very effective below-grade waterproofing system if:

- Appropriate products are specified and installed properly
- Soil testing is performed
- Quality control processes are implemented during construction



Thank You

Questions?

